

Unisys

DATE: March 13, 1998
TO: S. Hull/562
FROM: K. Sahu/S. Kniffin/300.1
SUBJECT: **Radiation Report on: OM11725SMX (Omnirel) (LDC 9735)**
Project: MAP/Subsystem
Job #: C80644
Project part #: OM11725 (OM7646)

PPM-98-002

cc: M. Delmont/303
A. Reyes/OSC
A. Sharma/311
OFA Library/300.1

A radiation evaluation was performed on **OM11725SMX Surface Mount Positive Adjustable 1.0Amp Voltage Regulator (Omnirel)** to determine the total dose tolerance of these parts. **This particular package is the hi-rel version of OM7646.** A brief summary of the test results is provided below. For detailed information, refer to Tables I through IV and Figure 1.

The total dose testing was performed using a Co⁶⁰ gamma ray source. During the radiation testing, four parts were irradiated under bias (see Figure 1 for bias configuration) and one part was used as a control sample. The total dose radiation levels were 5.0, 10.0, 15.0, 20.0, 30.0, 50.0, and 75.0 kRads.* The dose rate was between 0.125 and 0.500 kRads/hour (0.035 to 0.139 Rads/s). See Table II for the radiation schedule and effective dose rate calculation. The effective dose rate over all testing was 0.043 Rads/sec. After each radiation exposure and annealing treatment, parts were electrically tested according to the test conditions and the specification limits** listed in Table III.

Initial electrical measurements were made on 5 samples. Four samples (SN's 20, 21, 30, and 32) were used as radiation samples while SN 39 was used as a control sample. All parts passed all tests during initial electrical measurements.

All parts passed all tests up to 15 kRads.

After the 20.0 kRad irradiation, SN 30 had a catastrophic failure, exceeding the specification limits for vref by a factor of 10, vline_a by a factor of 1000, vline_by by a factor of 4, and vload by a factor of 1000. **All other parts passed all other tests.**

After the 30.0 kRad irradiation, SN 30 showed no significant change and was removed from further testing. **All parts passed all other tests.**

After the 50.0 kRad irradiation, SN's 20 and 32 fell below the specification limit of -9.0mV for vline_a with readings of -17.2 and -57.1mV respectively. SN 32 also fell below the specification limit of -5.0mV for vline_b with a reading of -6.4mV. **All parts passed all other tests.**

After the 75.0 kRad irradiation, SN 21 suffered a catastrophic failure in much the same way as SN 30. SN 32 fell marginally below the specification limit of 1.200V for vref with a reading of 1.198V, and fell below the specification limit for vline_b with a reading of -10.7mV. SN's 20 and 32 continued to fall below the specification limit for vline_a with readings of -18.8 and -66.9mV respectively. **All parts passed all other tests.**

* The term Rads, as used in this document, means Rads (silicon). All radiation levels cited are cumulative.

** These are manufacturer's pre-irradiation data specification limits. The manufacturer provided no post-irradiation limits at the time these tests were performed.

Table IV provides a summary of the test results with the mean and standard deviation values for each parameter after each irradiation exposure and annealing step.


Any further details about this evaluation can be obtained upon request. If you have any questions, please call me at (301) 731-8954.

ADVISORY ON THE USE OF THIS DOCUMENT

The information contained in this document has been developed solely for the purpose of providing general guidance to employees of the Goddard Space Flight Center (GSFC). This document may be distributed outside GSFC only as a courtesy to other government agencies and contractors. Any distribution of this document, or application or use of the information contained herein, is expressly conditional upon, and is subject to, the following understandings and limitations:

- (a) The information was developed for general guidance only and is subject to change at any time;
- (b) The information was developed under unique GSFC laboratory conditions that may differ substantially from outside conditions;
- (c) GSFC does not warrant the accuracy of the information when applied or used under other than unique GSFC laboratory conditions;
- (d) The information should not be construed as a representation of product performance by either GSFC or the manufacturer;
- (e) Neither the United States government nor any person acting on behalf of the United States government assumes any liability resulting from the application or use of the information.

Figure 1. Radiation Bias Circuit for OM11725SMX

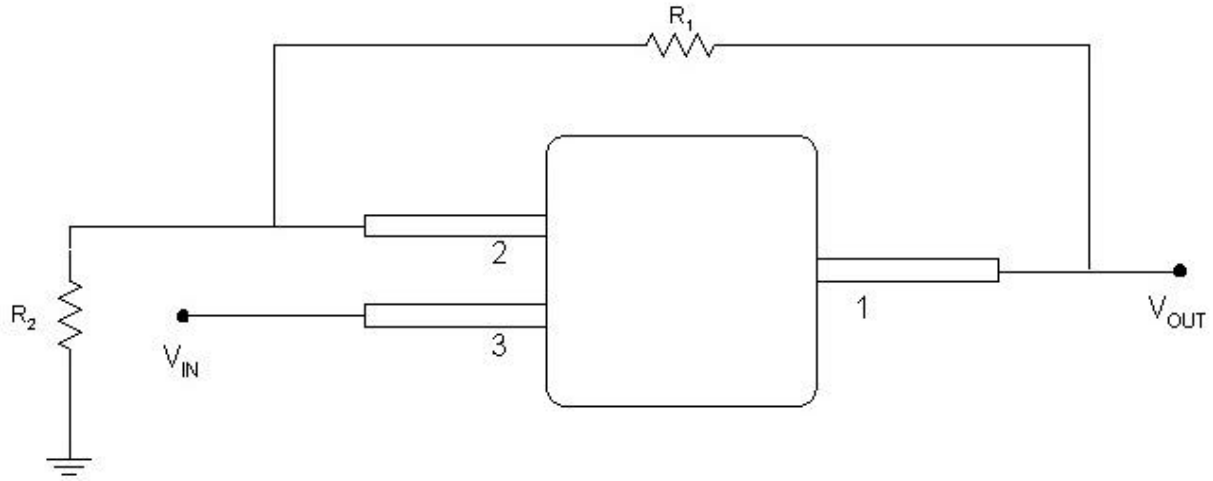

Notes:

1. Pin 1: V_{OUT} , Pin 2: Adjust, Pin 3: V_{IN} , Case: Isolated
2. $R_1 = 250\Omega \pm 5\%$ $\frac{1}{4}W$.
3. $R_2 = 5k\Omega \pm 5\%$ $\frac{1}{4}W$.
4. $V_{IN} = 35.0V \pm 0.5V$.
5. $V_{OUT} = 26.8V \pm 0.5V$.

TABLE I. Part Information

Generic Part Number:	OM11725SMX (OM7646)
MAP/Subsystem Part Number	OM11725SMX
Charge Number:	C80644
Manufacturer:	Omnirel
Lot Date Code (LDC):	9735
Quantity Tested:	15
Serial Number of Control Sample:	39
Serial Numbers of Radiation Samples:	20, 21, 30, and 32
Part Function:	Positive Adjustable 1.0Amp Voltage Regulator
Part Technology:	Bipolar
Package Style:	3 Pin Hermetic Isolated Surface Mount
Test Equipment:	A540
Test Engineer:	S. Archer-Davies

- No radiation tolerance/hardness was guaranteed by the manufacturer for this part.

TABLE II. Radiation Schedule for OM11725SMX

EVENT.....	DATE
1) INITIAL ELECTRICAL MEASUREMENTS	02/02/98
2) 5.0 KRAD IRRADIATION (0.062 KRADS/HOUR)	02/11/98
POST-5.0 KRAD ELECTRICAL MEASUREMENT	02/13/98
3) 10.0 KRAD IRRADIATION (0.062 KRADS/HOUR)	02/13/98
POST-10.0 KRAD ELECTRICAL MEASUREMENT	02/18/98
4) 15.0 KRAD IRRADIATION (0.125 KRADS/HOUR)	02/18/98
POST-15.0 KRAD ELECTRICAL MEASUREMENT	02/20/98
5) 20.0 KRAD IRRADIATION (0.125 KRADS/HOUR)	02/20/98
POST-20.0 KRAD ELECTRICAL MEASUREMENT	02/23/98
6) 30.0 KRAD IRRADIATION (0.250 KRADS/HOUR)	02/23/98
POST-30.0 KRAD ELECTRICAL MEASUREMENT	02/25/98
7) 50.0 KRAD IRRADIATION (0.500 KRADS/HOUR)	02/25/98
POST-50.0 KRAD ELECTRICAL MEASUREMENT	02/27/98
8) 75.0 KRAD IRRADIATION (0.500 KRADS/HOUR)	02/27/98
POST-75.0 KRAD ELECTRICAL MEASUREMENT	03/02/98

Effective Dose Rate = 75,000 RADS/20 DAYS=156.3 RADS/HOUR=0.043 RADS/SEC

PARTS WERE IRRADIATED AND ANNEALED UNDER BIAS, SEE FIGURE 1.

Table III. Electrical Characteristics of OM11725SMX /1

Test #	Parameter	Units	Test Conditions /2	Spec. min	Lim. max
1	iadj_1	mA	V _{DIFF} = 3.3V		100
2	iadj_2	mA	V _{DIFF} = 40V		100
3	iadj_3	mA	V _{DIFF} = 60V		100
4	delta_I	mA	V _{DIFF} = 3.0V, 10mA £I _L £195mA	-5.0	5.0
5	delta_I	mA	V _{DIFF} = 40V, 10mA £I _L £195mA	-5.0	5.0
6	vref	V	V _{DIFF} = 40V	1.200	1.300
7	vline_a	mV	3.0V £V _{DIFF} £40V, V _{OUT} = V _{REF}	-9.0	9.0
8	vline_b	mV	40V £V _{DIFF} £60V, V _{OUT} = V _{REF}	-5.0	5.0
9	vload	mV	V _{DIFF} = 40V, 10mA £I _L £195mA	-15.0	15.0
10	ilmin_3V	mA	V _{DIFF} = 3.0V, V _{OUT} = 1.4V (forced)	-5.0	5.0
11	ilmin_3.3V	mA	V _{DIFF} = 3.3V, V _{OUT} = 1.4V (forced)	-5.0	5.0
12	ilmin_40V	mA	V _{DIFF} = 40V, V _{OUT} = 1.4V (forced)	-5.0	5.0
13	ilmin_60V	mA	V _{DIFF} = 60V, V _{OUT} = 1.4V (forced)	-7.0	7.0

Notes:

1/ These limits are the manufacturer's non-irradiated data sheet specification limits. No post-irradiation limits were provided by the manufacturer at the time the tests were performed.

2/ I_L = 8mA unless otherwise specified.

TABLE IV: Summary of Electrical Measurements after Total Dose Exposures and Annealing for OM11725SMX /1

Test #	Parameters	Units	Spec. Lim. /2		Total Dose Exposure (kRads)															
					Initial		5.0		10.0		15.0		20.0 /3		30.0		50.0		75.0 /4 /5	
					mean	sd	mean	sd	mean	sd	mean	sd	mean	sd	mean	sd	mean	sd	mean	sd
1	Iadj_1	mA		100	-38	0.7	-39	0.8	-39	0.8	-38	0.8	-38	0.5	-38	0.5	-34	1.9	P	
2	Iadj_2	mA		100	-39	0.8	-38	0.8	-39	0.8	-39	0.9	-38	0.5	-38	0.5	-37	0.5	2P/1F	
3	Iadj_3	mA		100	-39	1.0	-39	0.07	-39	0.8	-39	0.8	-38	0.5	-38	0.5	-38	0.9	P	
4	delta_I	mA	-5.0	5.0	0.2	0.1	0.2	0.1	0.2	0.2	0.2	0.2	0.2	0	0.1	0.1	0	0.1	P	
5	delta_I	mA	-5.0	5.0	0.2	0.2	0.1	0.4	0.1	0.3	0.2	0.2	-0.1	0.05	-0.1	0.1	-0.3	0.1	P	
6	vref	V	1.200	1.300	1.252	0.004	1.251	0.004	1.250	0.004	1.246	0.004	1.243	0.004	1.241	0.005	1.219	0.012	1P/2F	
7	vline_a	mV	-9.0	9.0	-0.6	0.1	-0.6	0.1	-0.6	0.1	-0.7	0	-0.8	0.1	-1.4	0.3	-9.5	6.7	F	
8	vline_b	mV	-5.0	5.0	-0.9	0	-0.9	0.1	-1.0	0.1	-1.3	0.1	-1.5	0.1	-2.1	0.4	-3.4	2.5	F	
9	vload	mV	-15	15	1.7	0.1	2.0	0.1	2.1	0.2	2.2	0.1	2.4	0.1	3.0	0.1	4.2	3.5	1P/2F	
10	ilmin_3V	mA	-5.0	5.0	-1.0	0.1	-1.0	0.1	-1.0	0.1	-1.0	0.1	-1.0	0.1	-1.1	0	-0.3	0.5	P	
11	ilmin_3.3V	mA	-5.0	5.0	-1.0	0.1	-1.0	0.1	-1.0	0.1	-1.0	0.1	-1.0	0.1	-1.1	0	-0.3	0.5	P	
12	ilmin_40V	mA	-5.0	5.0	-1.8	0.1	-1.8	0.1	-1.8	0.1	-1.8	0.1	-1.8	0.1	-1.9	0	-1.9	0	P	
13	ilmin_60V	mA	-7.0	7.0	-2.4	0.1	-2.5	0.1	-2.5	0.1	-2.5	0.1	-2.5	0.1	-2.6	0.1	-2.6	0.1	P	

Notes:

- 1/ The mean and standard deviation values were calculated over the four parts irradiated in this testing. The control samples remained constant throughout testing and are not included in this table.
- 2/ These are manufacturer's pre-irradiation data sheet specification limits. No post-irradiation limits were provided by the manufacturer at the time the tests were performed.
- 3/ SN 30 failed catastrophically at this level and was removed from further consideration in the mean and standard deviation.
- 4/ SN 21 failed catastrophically at this level; we cannot supply a meaningful mean and standard deviation with only two parts.
- 5/ "P" ("F") implies all parts passed (failed) this test at this level. nPmF implies that "n" parts passed and "m" parts failed this test at this level.

Radiation sensitive parameters: vref, vline_a, vline_b, vload.